

Intracavity testing of KTP crystals for second harmonic generation at 532 nm

Hervé Albrecht, François Balembois, D. Lupinski, Patrick Georges, Alain Brun

► **To cite this version:**

Hervé Albrecht, François Balembois, D. Lupinski, Patrick Georges, Alain Brun. Intracavity testing of KTP crystals for second harmonic generation at 532 nm. Applied optics, Optical Society of America, 1999, 38 (12), pp.2536-2539. hal-00761393

HAL Id: hal-00761393

<https://hal-iogs.archives-ouvertes.fr/hal-00761393>

Submitted on 5 Dec 2012

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Intracavity testing of KTiOPO_4 crystals for second-harmonic generation at 532 nm

Hervé Albrecht, François Balembois, Dominique Lupinski, Patrick Georges, and Alain Brun

We have developed a diode-pumped Nd:YVO_4 cw laser for testing KTiOPO_4 crystals designed for intracavity second-harmonic generation at 532 nm. We demonstrate that this source is extremely sensitive to defects inside the crystal, inducing losses at 1064 nm and an index mismatch between fundamental and harmonic waves. © 1999 Optical Society of America

OCIS codes: 140.3480, 140.3580, 140.7300, 190.2620, 190.4400.

1. Introduction

KTiOPO_4 (KTP) nonlinear crystals are frequently used in numerous Nd-doped lasers emitting at 532 nm by second-harmonic generation.¹⁻⁴ Its excellent nonlinear properties make KTP particularly suitable for generating green light at 532 nm in cw operation up to the watt level. In this regime the KTP crystal is generally placed inside the laser cavity to increase the conversion efficiency. It is well known that the laser emission is highly sensitive to intracavity elements, in particular to induced losses.⁵ For a manufacturer of KTP crystals it is therefore extremely important to be able to evaluate crystal performances and homogeneity in an intracavity doubling configuration.

In this paper we describe a diode-pumped laser source designed for intracavity testing of KTP crystals cut for second-harmonic generation at 532 nm. We identify defects in KTP crystals by using this testing bench and discuss the advantages of using this source for testing KTP crystals compared with use of an extracavity testing bench.

2. Description of the Intracavity KTP Tester

We have designed a diode-pumped laser source inside which the KTP crystal can be easily installed for

rapid testing. All the KTP crystals tested were cut for second-harmonic generation at 532 nm, with plane and parallel faces normal to the phase-matching direction. The experimental setup is described in Fig. 1. We used a laser diode with an output facet area of $500 \mu\text{m}$ by $1 \mu\text{m}$, emitting 4 W of power at 808 nm (SDL 2380-P1). The output beam was collimated and focused by two high-numerical-aperture (N.A. of 0.5) objectives (O_1 and O_2), with 8-mm focal length. An anamorphic prism pair with $3\times$ magnification reshaped the pump beam in the direction parallel to the diode junction. With these optics, the pump beam spot was reduced to $170 \mu\text{m}$ inside the gain medium (Nd:YVO_4). The laser cavity consisted of four mirrors with high-reflection coating at 1064 nm. Mirror M_1 was directly coated onto a 1-mm-long, 1.1% doped Nd:YVO_4 crystal. M_2 was a concave mirror with radius of curvature of 200 mm. With this value, the beam waist inside the Nd:YVO_4 crystal was $190 \mu\text{m}$ (diameter), wide enough to overlap the pump beam. M_3 and M_4 were also concave mirrors with radii of curvature of 150 and 100 mm, respectively. These values were chosen to have relatively high conversion efficiency at 532 nm and to be easily installable upon the KTP crystal. The KTP crystal was placed at the waist position between M_3 and M_4 , where the spot size, determined by M_3 radius of curvature, was $140 \mu\text{m}$ (diameter). The distance between the KTP and M_3 was approximately 75 mm, and it was approximately 100 mm between the KTP and M_4 . So there would be only one output in the green, M_4 was high-reflection coated at 532 nm and M_3 was antireflection coated at 532 nm. To test the crystal homogeneity we mounted the KTP crystal upon two translation stages moving perpendicularly to the optical cavity axis.

To obtain stable green output power we chose a

H. Albrecht and D. Lupinski are with Cristal Laser, 12 allée J. Rostand, B.P. 44, 54230 Chaligny, France. F. Balembois, P. Georges, and A. Brun are with the Laboratoire Charles Fabry de l'Institut d'Optique, B.P. 147, 91403 Orsay Cedex, France. The e-mail address for F. Balembois is francois.balembois@iota.u-psud.fr.

Received 30 September 1998; revised manuscript received 4 January 1999.

0003-6935/99/122536-04\$15.00/0

© 1999 Optical Society of America

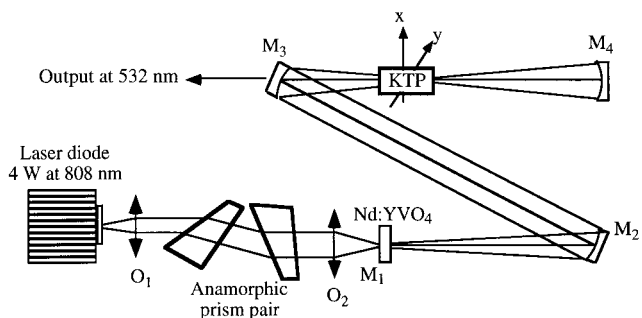


Fig. 1. Experimental setup for intracavity testing.

relatively long cavity (110 cm) such that the laser emitted many axial modes. In this regime, sum-frequency effects between adjacent longitudinal modes at 1064 nm (the so-called green problem⁶) are averaged.⁷ We recorded the green output power for a 5-mm-long reference crystal, antireflection coated at 1064 and 532 nm with a thermal detector (bolometer) during 15 min. (Fig. 2). We obtained 300 mW of output power with a good stability (1.5% rms). Part a of Fig. 3 presents the same experiment but with an uncoated reference crystal. One can observe that there the output power was much less stable (9% rms). To understand this difference one has to consider the high Fresnel reflection coefficient (8% at 1064 nm) for the uncoated faces of the KTP. Instabilities induced by end faces of crystals perfectly

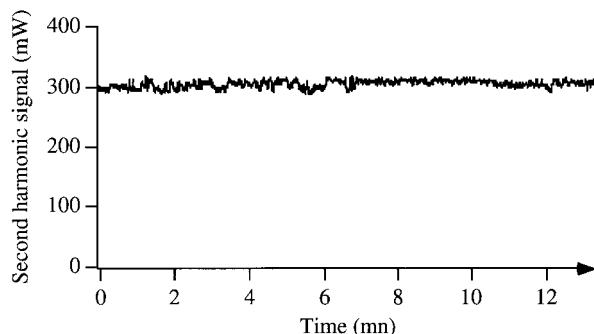


Fig. 2. Output power at 532 nm as a function of time for an antireflection-coated KTP crystal in the intracavity tester.

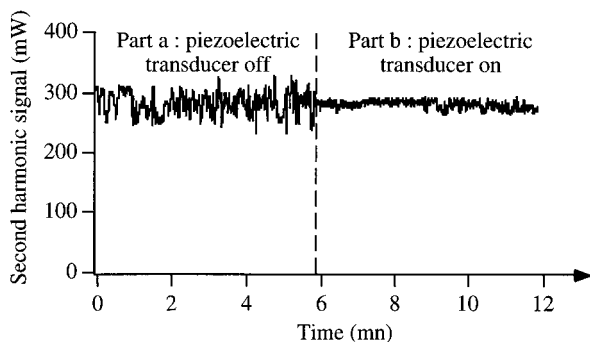


Fig. 3. Stability for an uncoated KTP crystal when the piezoelectric transducer was off and on.

perpendicular to the cavity axis have already been observed in intracavity frequency-doubled lasers.^{7,8} Two explanations for this phenomenon can be given: First, as the faces were plane and parallel, the KTP acted as an intracavity Fabry–Perot etalon, reducing the number of longitudinal modes and so increasing the instabilities induced by the mode coupling by sum-frequency generation.⁷ The second explanation comes from the phase-locking process of the longitudinal modes that plays a role in stabilizing the green output power.⁸ This process was perturbed by the mode frequency shift caused by the uncoated faces of the KTP crystal at normal incidence.

For manufacturers involved in the nonlinear crystals market, testing the conversion efficiency of uncoated pieces just after cutting and polishing is highly appropriate. To achieve this testing it is necessary to use a laser source with stable output during the entire test. To improve the stability of the output signal with uncoated KTP crystals we mounted mirror M_4 onto a piezoelectric transducer, which was driven with a square electrical signal of 20-V amplitude (peak to peak) and 1-kHz frequency. We estimated the displacement of mirror M_4 to be $\sim 0.5 \mu\text{m}$. As the cavity length moved at a frequency of 1 kHz, the interference effects induced by coupled cavities were also at the same or a higher frequency. Thus the instabilities in output power were moved from a scale of seconds to one of milliseconds. As the time response of our detector (bolometer) was ~ 0.1 s, the output fluctuations recorded by our detector were smaller when the piezoelectric transducer was on. Part b of Fig. 3 shows that we obtained fluctuations of 2% rms, as opposed to 9% rms when the piezoelectric transducer was off.

Another problem in intracavity doubling comes from possibly ambiguous results between low-loss operation of the laser when the KTP uncoated faces are exactly perpendicular to the cavity axis and the higher conversion efficiency off axis if the KTP phase-matching direction is not perfectly perpendicular to the crystal faces. In fact, we found that the green output power depended strongly on the KTP orientation. To test the different KTP crystals under exactly the same conditions in the cavity we carefully oriented the crystal faces perpendicular to the optical cavity axis. After that, the crystal orientation was never modified. We regulated the crystal in temperature to adjust the phase-matching direction perfectly parallel to the cavity axis. To prove that temperature adjustment allowed the phase-matching direction to be realigned with the cavity axis, we used two reference KTP crystals that had different phase-matching directions relative to their faces: 0.08° for the first crystal and 0.98° for the second. After temperature adjustments (to 24.4°C for the first crystal and to 46.5°C for the second), we obtained approximately the same output power from the two crystals (290 and 280 mW, respectively).

By the method described above, we could obtain reliable information about the quality of KTP crystals.

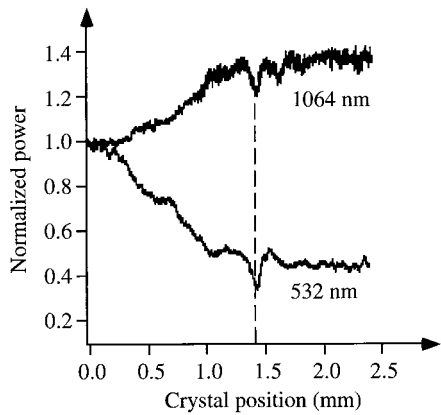


Fig. 4. Comparison of normalized power at 1064 and 532 nm in the intracavity configuration for a specific test crystal.

3. Identification of Defects in KTP

Two kinds of defect may decrease the green output power in a laser source that uses a KTP crystal. The first are localized defects in the bulk material or at the surface (dusts or streaks), which induce losses inside the laser cavity. Such additional intracavity losses cause the IR intracavity power and thus the green output power to decrease. The second kind of defect is index inhomogeneities at fundamental or harmonic wavelengths. These inhomogeneities lead to changes in the phase-matching conditions for efficient second-harmonic generation. So the IR intracavity power is not directly affected by these defects but the green output power can be strongly affected even by a small index inhomogeneity.

A simple method to identify these two kinds of defect is to record the IR power leakage at mirror M_2 and the green output at the same time. We did this for a crystal that had these two kinds of defect. Figure 4 shows a scan along the X axis (defined in Fig. 1). The IR and green powers were normalized at the abscissa $x = 0$. At position $x = 1.4$ mm we observed a decrease in both IR and green power. This fact could be attributed to losses induced by a localized defect. From $x = 0$ to $x = 2.5$ mm we observed a smooth decrease in the green output power, whereas the IR power increased. This behavior could be attributed not to localized defects but to index variations. At $x = 0$ the green output power was high (280 mW). This corresponded to high nonlinear output coupling for the laser cavity⁵ and thus to moderate intracavity power (~ 5 W) at 1064 nm. At $x = 2.5$ mm, the green output was low. A phase mismatch between fundamental and harmonic waves induced a decrease in the green output, a decrease in the nonlinear output coupling for the laser cavity, and thus an increase in IR intracavity power (~ 8 W).

4. Advantages of Intracavity Testing

Traditionally, the efficiency of nonlinear second-harmonic crystals has been tested with energetic nanosecond pulses at the fundamental wavelength. In this case, the peak power was high enough that a

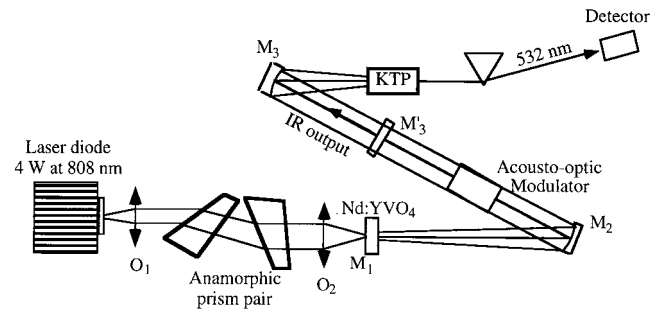


Fig. 5. Experimental setup for extracavity testing.

simpler extracavity experimental scheme could be used. Therefore it is important to compare the sensitivity of our intracavity source with that of an extracavity testing bench.

To do so, we modified our laser source and developed a diode-pumped Q -switched Nd:YVO₄ laser based on the same pumping scheme (Fig. 5). The laser cavity consisted of three mirrors, M_1 , M_2 , and M_3 . M_1 and M_2 were the same as before. M_3 was a plane output mirror with 30% transmission at 1064 nm. An acousto-optic modulator was inserted into the collimated arm of the cavity, between M_2 and M_3 . The laser operated at a 30-kHz repetition rate and emitted 150-ns pulses with 500-mW average power (corresponding to a peak power of 110 W at 1064 nm). The output beam was focused in the KTP by mirror M_3 described above. A prism separated the green and the fundamental beams. The average output power reached 3 mW at 532 nm for 5-mm-long KTP crystals. With the experimental schemes described in Figs. 1 and 5 we were able to scan the same crystal in the extracavity and the intracavity configurations at the same place and with the same spot size for the fundamental beam. To compare the two testing benches we used the same specific crystal as previously. Figure 6 shows the normalized green output power versus the crystal position for the two configurations. In the extracavity scheme one can see a very small decrease, corresponding to the index mismatch observed previously. Moreover, the localized defect at $x = 1.4$ mm is absolutely invisible.

These experiments demonstrate the much greater sensitivity to losses and to index mismatch of the

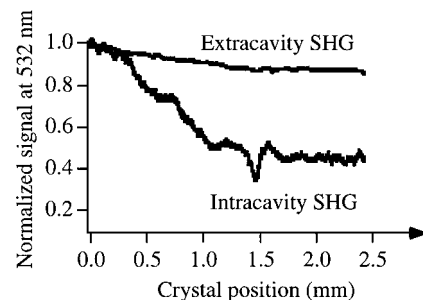


Fig. 6. Comparison of second-harmonic generation (SHG) in intracavity and extracavity testing for the same crystal as in Fig. 4.

intracavity configuration compared with the extracavity configuration.

5. Conclusions

In this study we demonstrated that, compared with extracavity testing, intracavity testing of KTP is more sensitive to index mismatch and much more sensitive to the small localized defects that induce losses. We have also identified the signatures of the defects that decrease conversion efficiency: Residual losses are local and induce a sharp decrease in conversion efficiency, whereas index mismatch induces a smaller and smoother decrease in green output power.

In conclusion, we have proved that intracavity testing is a suitable tool for qualifying KTP crystals for intracavity second-harmonic generation at 532 nm. It can provide to the customer, who integrates the crystal into a laser system, relevant data regarding crystal homogeneity. This is a key test to determine whether a crystal meets the customer's specifications.

This research was partially supported by the groupement de recherches "Lasmat" from the Centre National de la Recherche Scientifique.

References

1. D. W. Anthon, D. L. Sipes, T. J. Pier, and M. R. Ressler, "Intracavity doubling of cw diode-pumped Nd:YAG lasers with KTP," *IEEE J. Quantum Electron.* **28**, 1148–1157 (1992).
2. L. R. Marshall, A. D. Hays, A. Kaz, and R. L. Burnham, "Intracavity doubled mode-locked and cw diode-pumped lasers," *IEEE J. Quantum Electron.* **28**, 1158–1163 (1992).
3. H. Hemmati and J. R. Lesh, "High repetition rate Q-switched and intracavity doubled diode-pumped Nd:YAG laser," *IEEE J. Quantum Electron.* **28**, 1018–1020 (1992).
4. N. MacKinnon and B. D. Sinclair, "A laser diode array pumped, Nd:YVO₄/KTP, composite material microchip laser," *Opt. Commun.* **105**, 183–187 (1994).
5. R. G. Smith, "Theory of intracavity optical second-harmonic generation," *IEEE J. Quantum Electron.* **6**, 215–223 (1970).
6. T. Baer, "Large-amplitude fluctuations due to longitudinal mode coupling in diode-pumped intracavity-doubled Nd:YAG lasers," *J. Opt. Soc. Am.* **3**, 1175–1180 (1986).
7. V. Magni, G. Cerullo, S. De Silvestri, O. Svelto, L. J. Qian, and M. Danailov, "Intracavity frequency doubling of a cw high-power TEM₀₀ Nd:YLF laser," *Opt. Lett.* **18**, 2111–2113 (1993).
8. M. Tsunekane, N. Taguchi, and H. Inaba, "Elimination of chaos in a multilongitudinal-mode, diode-pumped, 6-W continuous-wave, intracavity-doubled Nd:YAG laser," *Opt. Lett.* **22**, 1000–1002 (1997).